

## Solutions

Mole fraction of component A =  $x_A$

Mass Fraction of component A =  $m_A$

Volume Fraction of component A =  $\phi_A$

Typically we make a binary blend, A + B, with mass fraction,  $m_A$ , and want volume fraction,  $\phi_A$ , or mole fraction,  $x_A$ .

$$\phi_A = (m_A/\rho_A)/((m_A/\rho_A) + (m_B/\rho_B))$$

$$x_A = (m_A/MW_A)/((m_A/MW_A) + (m_B/MW_B))$$

## Solutions

$$\begin{array}{l} -S \quad U \quad V \\ H \quad A \\ -p \quad G \quad T \end{array}$$

$$\mathbf{G = H - TS} \quad \mathbf{A = U - ST} \quad \mathbf{U = H - PV}$$

**Need the Entropy S**

Three ways to get entropy and free energy of mixing

- A) Isothermal free energy expression, pressure expression
- B) Isothermal volume expansion approach, volume expression
- C) From statistical thermodynamics

### A. Pressure Expression: Mix two ideal gasses, A and B

$$p = p_A + p_B \quad p_A \text{ is the partial pressure } p_A = x_A p$$

$$\begin{matrix} -S & U & V \\ H & A \\ -p & G & T \end{matrix}$$

For single component molar  $G = \mu$

$\mu_0$  is at  $p_{0,A} = 1 \text{ bar}$

At pressure  $p_A$  for a pure component isothermal ideal gas

$$\mu_A = \mu_{0,A} + RT \ln(p/p_{0,A}) = \mu_{0,A} + RT \ln(p)$$

$$\begin{aligned} dG &= -SdT + Vdp \\ \text{Isothermal and Ideal Gas} \\ dG &= RTdp/p \\ G &= RT \ln(p/p_0) \end{aligned}$$

For a mixture of A and B with a total pressure  $p_{\text{tot}} = p_{0,A} = 1 \text{ bar}$  and  $p_A = x_A p_{\text{tot}}$

For component A in a binary mixture

$$\mu_A(x_A) = \mu_{0,A} + RT \ln(x_A p_{\text{tot}}/p_{0,A}) = \mu_{0,A} + RT \ln(x_A) \quad \text{Isothermal ideal gas (no enthalpy)}$$

Notice that  $x_A$  must be less than or equal to 1, so  $\ln x_A$  must be negative or 0

So, the chemical potential must drop in the solution for a solution to exist.

Ideal gasses only have entropy so entropy drives mixing in this case.

This can be written,  $x_A = \exp((\mu_A(x_A) - \mu_{0,A})/RT)$

Which indicates that  $x_A$  is the Boltzmann probability of finding A

**Mix two real gasses, A and B**

$$\mu_A(x_A) = \mu_A^o + RT \ln \left( \frac{f_A}{p_A^o} \right) = \mu_A^o + RT \ln(f_A) \quad \text{Gas}$$

$$\mu_A = \mu_A^* + RT \ln a_A \quad \text{Solution}$$

$$\mu_A^* = \mu_{0,A} \text{ if } p = 1$$

## Solutions

$$\begin{array}{l} -S \quad U \quad V \\ H \quad A \\ -p \quad G \quad T \end{array}$$

$$\mathbf{G = H - TS} \quad \mathbf{A = U - ST} \quad \mathbf{U = H - PV}$$

**Need the Entropy S**

Three ways to get entropy and free energy of mixing

- A) Isothermal free energy expression, pressure expression
- B) Isothermal volume expansion approach, volume expression
- C) From statistical thermodynamics

## B. Volume Expression: Ideal Gas Mixing

For isothermal  $\Delta U = C_V dT = 0 = dQ + dW$

$$dQ = -dW = pdV$$

For ideal gas  $dQ = -dW = nRT \ln(V_f/V_i)$

$$dQ = \Delta S/T$$

$$\Delta S = nR \ln(V_f/V_i)$$

Consider a process of expansion of a gas from  $V_A$  to  $V_{\text{tot}}$

The change in entropy is  $\Delta S_A = n_A R \ln(V_{\text{tot}}/V_A) = -n_A R \ln(V_A/V_{\text{tot}})$

Consider an isochoric mixing process of ideal gasses A and B.

A is originally in  $V_A$  and B in  $V_B$

$V_{\text{tot}}$  is  $V_A + V_B$

The change in entropy for mixing of A and B is

$$\Delta S_{\text{mixing A and B}} = -n_A R \ln(V_A/V_{\text{tot}}) - n_B R \ln(V_B/V_{\text{tot}}) = -nR(x_A \ln x_A + x_B \ln x_B)$$

For an isothermal, isochoric mixture of ideal gasses (also isobaric since  $P \sim T/V$ )

For ideal gasses  $\Delta H_{\text{mixing}} = 0$  since there is no interaction

$$\Delta G_{\text{mixing}} = \Delta H_{\text{mixing}} - T\Delta S_{\text{mixing}} = -T\Delta S_{\text{mixing}} = nRT(\ln x_A + \ln x_B)$$

So, the molar Gibbs Free energy for mixing is  $\Delta G_{\text{mixing}} = RT(x_A \ln x_A + x_B \ln x_B)$

$$\begin{matrix} -S & U & V \\ H & A \\ -p & G & T \end{matrix}$$

$$\begin{aligned} dU &= -pdV + TdS \\ \text{Isothermal and Ideal Gas} \\ dG &= RTdp/p \end{aligned}$$

## Solutions

$$\begin{array}{l} -S \quad U \quad V \\ H \quad A \\ -p \quad G \quad T \end{array}$$

$$\mathbf{G = H - TS} \quad \mathbf{A = U - ST} \quad \mathbf{U = H - PV}$$

**Need the Entropy S**

Three ways to get entropy and free energy of mixing

- A) Isothermal free energy expression, pressure expression
- B) Isothermal volume expansion approach, volume expression
- C) From statistical thermodynamics

### C. Statistical Thermodynamics

Boltzmann's Law:  $\Delta S = k_B \ln \Omega$

$\Omega$  Is the number of states

For mixing of  $n_A$  and  $n_B$  with  $n$  total molecules

$$\Omega = n! / (n_A! n_B!)$$

Sterling's approximation for large  $n$ ,  $n! \sim n \ln(n) - n$

We assume that  $n$  is large then

$$\ln \Omega = -(n_A \ln(n_A/n) + n_B \ln(n_B/n))$$

$$\Delta S = -k_B (n_A \ln(n_A/n) + n_B \ln(n_B/n)) = -nk_B (x_A \ln(x_A) + x_B \ln(x_B))$$

$$\Delta G_{\text{mixing}} = \Delta H_{\text{mixing}} - T\Delta S_{\text{mixing}} = -T\Delta S_{\text{mixing}} = nRT(x_A \ln x_A + x_B \ln x_B)$$



## **Some Types of Entropy**

Thermodynamic entropy measured experimentally,  $Q/T$

### **Configurational also called Combinatorial**

Conformational

Translational and Rotational Entropy (Brownian motion)

Vibrational entropy

Conformational entropy computed in internal or Cartesian coordinates  
(which can even be different from each other)

Conformational entropy computed on a lattice

Entropy associated with organization on mixing (Hydrophobic effect and many other unexpected features on mixing)

**An “Ideal Solution” means:**

The change on mixing:

$$\Delta S = -nk_B (x_A \ln(x_A) + x_B \ln(x_B))$$

Since  $(\ln x)$  is always negative or 0,  $\Delta S$  is always positive for ideal solutions

$$\Delta G = -T \Delta S$$

Since  $(\ln x)$  is always negative or 0,  $\Delta G$  is always negative (or 0) and ideal solutions **always mix**

$\Delta H$  is 0, there is no interaction in ideal mixtures, there is no excluded volume, particles are ghosts to each other

$\Delta V = (d\Delta G/dp)_T = 0$ , there is no loss or gain of volume compared to the summed volume

Boltzmann Probability of a Thermally Reversible Event =  $\exp(-\Delta G/kT)$

$\Delta G$  is the change in free energy for the event

$\Delta G = \Delta H - T\Delta S$  (Const.  $T$  &  $P$ , e.g. an experimental measurement)

$\Delta A = \Delta U - T\Delta S$  (Const.  $T$  &  $V$ , e.g. a simulation on a grid)

Consider an ideal gas with no enthalpic interactions,  $\Delta H = 0$

The probability of finding an atom A in a mixture of A and B is the molar concentration  $x_A$

$\Delta S_A/k = -\ln x_A$  from the Boltzmann probability

and

$\Delta S/k = -x_A \ln x_A - x_B \ln x_B$  by a rule of random mixtures

$\Delta G_{\text{ideal}}/kT = x_A \ln x_A + x_B \ln x_B$  this is always negative since “ln” of a number less than 1 is negative, so mixing always reduces the free energy so *it always occurs for an ideal mixture*

**Hildebrandt Real Solution model** considers binary interactions.

The odds of a binary interaction of A and B is  $x_A x_B$

This interaction has an average enthalpy (or internal energy)  $\Delta H = x_A x_B \Omega_{AB}$  or  $x_1 x_2 A_{12}$

Where the first term is the Hildebrandt binary interaction parameter and the second is the Margules one-parameter interaction term. For polymers  $\chi_{12}$  is used, the Flory –Huggins interaction parameter (with a few modifications).

$$\Delta G_{\text{real solution}}/kT = x_1 \ln x_1 + x_2 \ln x_2 + x_1 x_2 A_{12} = x_1 \ln a_1 + x_2 \ln a_2 = x_1 \ln \gamma_1 x_1 + x_2 \ln \gamma_2 x_2$$

$$\Delta H /kT = \Delta G_{\text{excess}} /kT = x_1 x_2 A_{12} = x_1 \ln \gamma_1 + x_2 \ln \gamma_2$$


## Activity Coefficients as Derivatives

$$G^E = RT \sum_i x_i \ln(\gamma_i) \quad \text{Excess free energy per mole}$$

$G^E$  is the excess free energy value, so  $nG^E$

The excess chemical potential of component “i” in phase L or V,  $\mu_i^E$  is given by

$$\left( \frac{\partial G^E}{\partial n_i} \right)_{T, P, n_{j \neq i}} = \bar{G}_i^E = \mu_i^E = RT \ln \gamma_i$$

11.28  Activity coefficients are related to the partial molar excess Gibbs energy.

$$\frac{G^E}{RT} = A_{12}x_1x_2 \quad \frac{G^E}{RT} = n(A_{12}x_1x_2) = (A_{12}n_2)\left(\frac{n_1}{n}\right) \quad 11.29$$

$$\frac{1}{RT} \left( \frac{\partial G^E}{\partial n_1} \right)_{T, P, n_2} = \ln \gamma_1 = A n_2 \left[ \frac{1}{n} - \frac{n_1}{n^2} \right] = A \frac{n_2}{n} \left[ 1 - \frac{n_1}{n} \right] = A x_2 (1 - x_1) \quad 11.30$$

$$\ln \gamma_1 = A x_2^2 \quad ; \text{ similarly } \ln \gamma_2 = A x_1^2 \quad 11.31$$

This is how you can find the activity coefficients from the Margules one-parameter coefficient (or the Hildebrandt or Flory-Huggins interaction parameters)

## Real Solutions

### Molar excess functions or departure functions:


Difference between real value and ideal value

$$\text{Excess } \Delta G_{\text{mixing}} = \Delta G_{\text{mixing}} - RT(x_A \ln x_A + x_A \ln x_B)$$

$$\text{Excess } \Delta S_{\text{mixing}} = \Delta S_{\text{mixing}} + R(x_A \ln x_A + x_A \ln x_B)$$

$$\text{Excess } \Delta H_{\text{mixing}} = \Delta H_{\text{mixing}}$$

$$\text{Excess } \Delta V_{\text{mixing}} = \Delta V_{\text{mixing}}$$

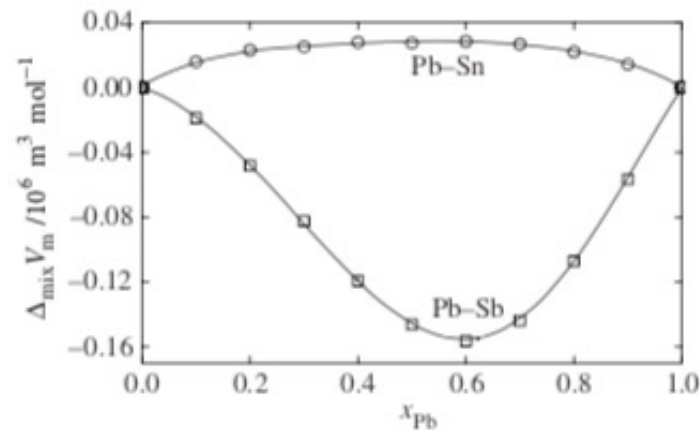

**Figure 3.2** Molar volume of mixing of molten Pb–Sn at 1040 K [1] and Pb–Sb at 907 K [2] as a function of composition.

## Real Solutions

$x_A$  becomes  $a_A$  the activity so

$$\Delta G_{\text{mixing}} = RT(x_A \ln a_A + x_B \ln a_B)$$


$$\begin{aligned}\text{Excess } \Delta G_{\text{mixing}} &= \Delta G_{\text{mixing}} - RT(x_A \ln x_A + x_B \ln x_B) \\ &= RT(x_A \ln(a_A/x_A) + x_B \ln(a_B/x_B)) \\ &= RT(x_A \ln(\gamma_A) + x_B \ln(\gamma_B))\end{aligned}$$

$\gamma$  is the activity coefficient


$$\text{Excess } \Delta S_{\text{mixing}} = -R(x_A \ln(\gamma_A) + x_B \ln(\gamma_B))$$

Method to use departure functions for calculations (PREOS.xls)

- 1) Calculation of properties in the ideal state is simple
- 2) With an equation of state the departure function can be calculated
- 3) For any transition first calculate the departure function to the ideal state
- 4) Then carry out the desired change as an ideal mixture or gas
- 5) Then use the departure function to return to the real state

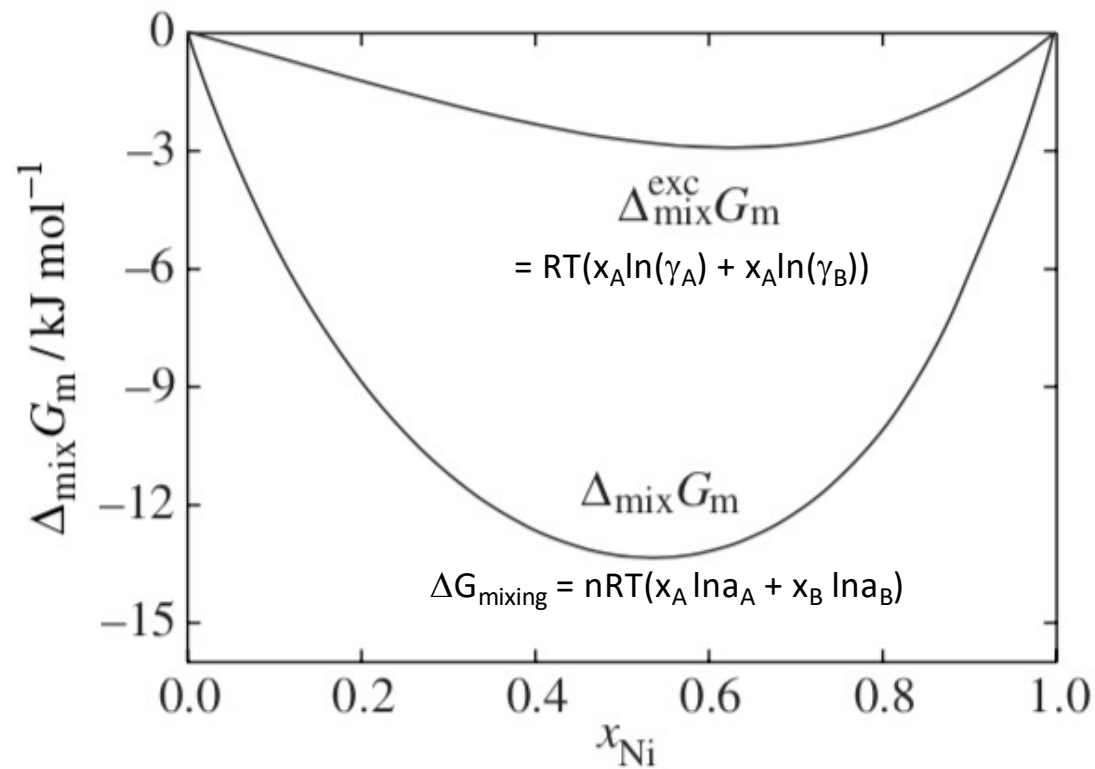

**Figure 3.5** The molar Gibbs energy of mixing and the molar excess Gibbs energy of mixing of molten Fe–Ni at 1850 K. Data are taken from reference [3].

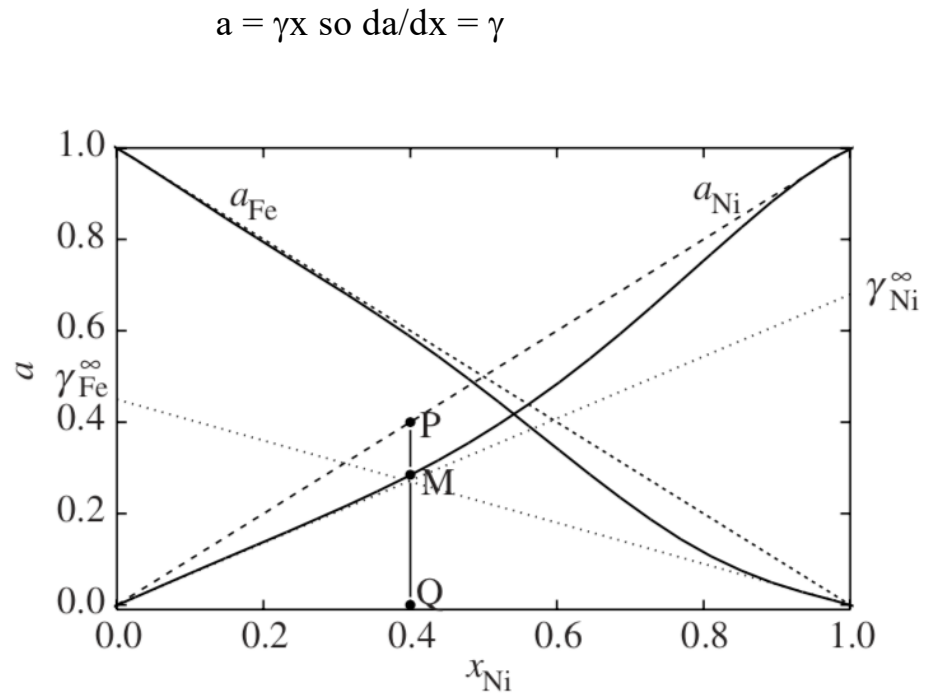


Get the activity coefficient at infinite dilution by extrapolating the slope for pure component to  $x = 0$ . This is used for Henry's Law and a few other places.

(Activity coefficient is  $a/x$ )

**Figure 3.4** The activity of Fe and Ni of molten Fe–Ni at 1850 K [3]. At  $x_{\text{Ni}} = 0.4$  the activity coefficient of Ni is given by  $MQ/PQ$ .



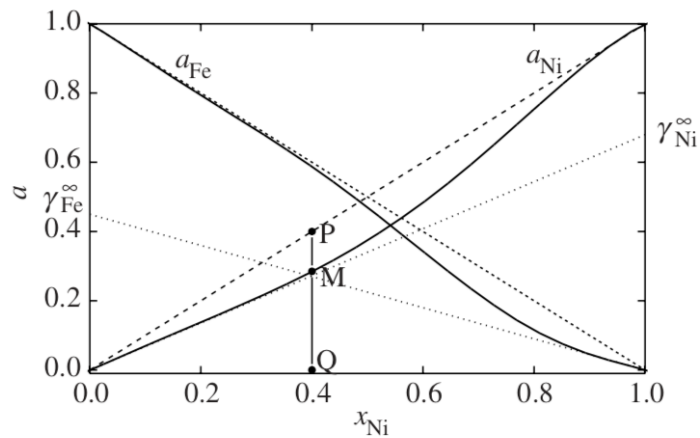

**Figure 3.4** The activity of Fe and Ni of molten Fe–Ni at 1850 K [3]. At  $x_{\text{Ni}} = 0.4$  the activity coefficient of Ni is given by  $\text{MQ}/\text{PQ}$ .

We want the infinite dilution activity coefficients to write a function to predict the activity and the activity coefficient.

This is one of the parameters for the functions.

With the a function for activity we can predict the free energy and the miscibility.

## Solute

### Henry's law for dilute solutions

Vapor pressure of solute =  $k_i x_i$

$k_i$  is the **Henry's Law Constant**

$x_i$  is the solute molar fraction (low  $\sim 0$ )

## Solvent or ideal mixture

### Raoult's Law for solvent or ideal mixtures

Vapor pressure =  $p^* x_j$

$x_j$  is the solvent molar fraction (high  $\sim 1$ )

$p^*$  is the vapor pressure of the pure solvent

If a solution is ideal, then  $x_A = a_A$  and  $\gamma_A = 1$

At infinite dilution a solvent is ideal (follows Raoult's law) so

$$(da_A/dx_A)_{x_A \rightarrow 1} = 1 = (d\gamma_A x_A/dx_A)_{x_A \rightarrow 1} = \gamma_A + x_A(d\gamma_A/dx_A)_{x_A \rightarrow 1}$$

But  $\gamma_A = 1$  at  $x_A = 1$ , then **Raoult's law** is followed if

$$(d\gamma_A/dx_A)_{x_A \rightarrow 1} = 0 \quad (\text{See next slide})$$

A solute follows **Henry's Law** if


$$(da_B/dx_B)_{x_B \rightarrow 0} = \gamma_B \text{ infinite dilution}$$

$$= (d\gamma_B x_B/dx_B)_{x_B \rightarrow 0} = (\gamma_B + x_B(d\gamma_B/dx_B))_{x_B \rightarrow 0}$$

So

$$(x_B(d\gamma_B/dx_B))_{x_B \rightarrow 0} = 0$$

This isn't that useful

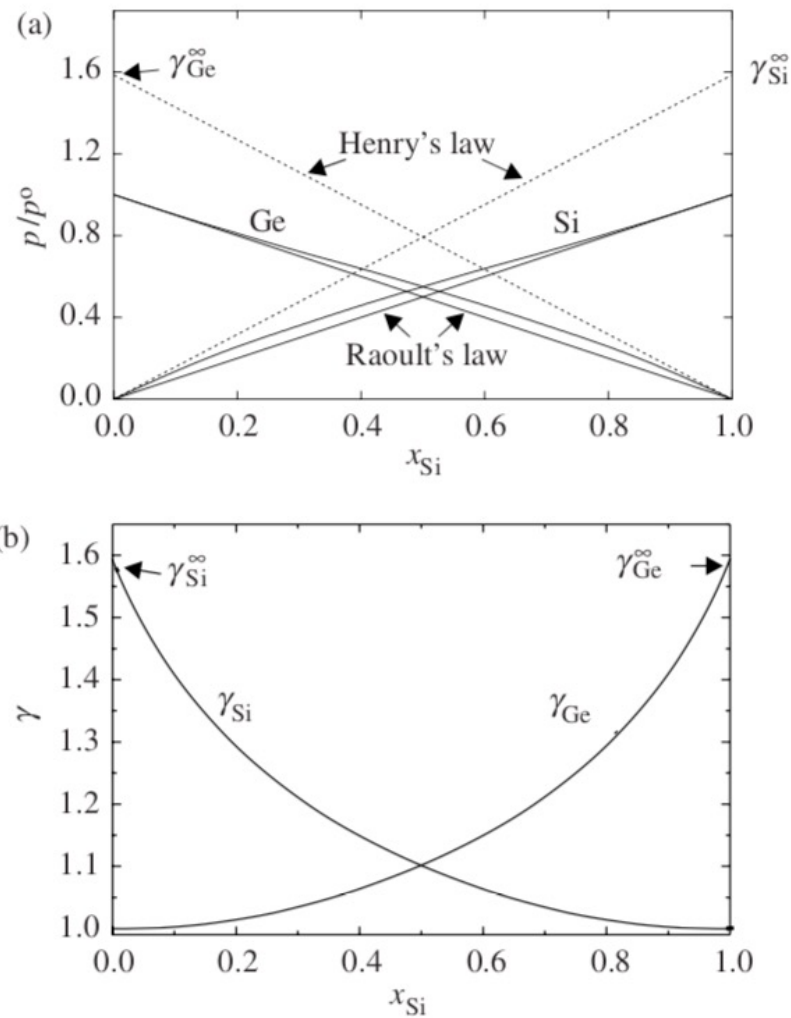


**Henry's law** for dilute solutions  
Vapor pressure of solute =  $k_i x_i$

**Raoult's Law** for solvent or ideal mixtures  
Vapor pressure =  $p^* x_j$

**Figure 3.6** (a) The vapour pressure above molten Si–Ge at 1723 K [4]. (b) The corresponding activity coefficients of the two components.

Activity of a component in a solution must be defined relative to a standard state, either Henrian (extrapolated) or Raoultian (measured,  $x = 1 :: a = 1$ )

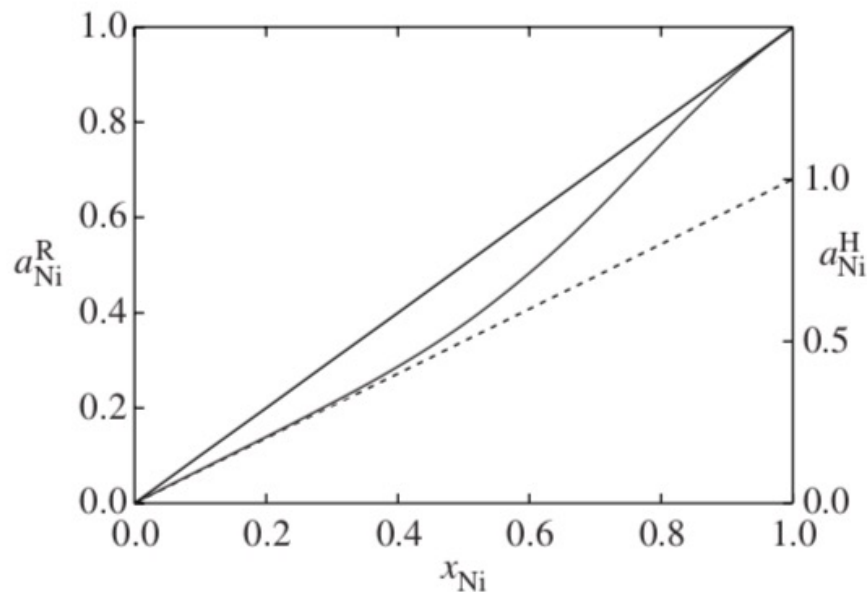

**Figure 3.7** The activity of Ni of molten Fe–Ni at 1850 K using both a Raoultian and a Henrian standard state. Data are taken from reference [3].

**You would use Henrian standard state if the solute had limited solubility like PCBs or oil in water and you wanted the infinite dilution of the water component**

The activities on the two standard states are related since

$$\mu_i = \mu_i^R + RT \ln a_i^R = \mu_i^H + RT \ln a_i^H$$

which gives

$$\frac{a_i^R}{a_i^H} = \exp \left[ -\frac{(\mu_i^R - \mu_i^H)}{RT} \right]$$

## Analytic Solution Models

Want to calculate the miscibility of components

Need to generate a phase diagram

Calculation of the vapor pressure

Simplest approach could be a polynomial. However, this generally doesn't inherently have any real meaning. The polynomial just reproduces existing data within experimental limits. Extrapolation is dangerous.

$$Y(x_B) = Q_0 + Q_1 x_B + Q_2 x_B^2 + \dots + Q_n x_B^n = \sum_{i=0}^n Q_i x_B^i$$

Asymmetric feature: vapor pressure

or

$$Y(x_B) = x_A x_B \sum_{i=0}^n R_i (x_A - x_B)^i = x_B (1 - x_B) \sum_{i=0}^n R_i (1 - 2x_B)^i$$

Symmetric Feature: Phase behavior

$$\ln \gamma_B = \ln \gamma_B^\infty + \left( \frac{\partial \ln \gamma_B}{\partial x_B} \right)_{x_B \rightarrow 0} x_B + \frac{1}{2} \left( \frac{\partial^2 \ln \gamma_B}{\partial x_B^2} \right)_{x_B \rightarrow 0} x_B^2 + \dots$$

$$+ \frac{1}{i!} \left( \frac{\partial^i \ln \gamma_B}{\partial x_B^i} \right)_{x_B \rightarrow 0} x_B^i$$

$$\ln \gamma_B = \sum_{i=0}^n J_i^B x_B^i$$

$$J_i^B = \frac{1}{i!} \left( \frac{\partial^i \ln \gamma_B}{\partial x_B^i} \right)_{x_B \rightarrow 0}$$

Interaction coefficients


Zeroth order infinite dilution (trivial)

First order  $\varepsilon_1^B$  self-interaction coefficient


$$\ln \gamma_B = \ln \gamma_B^\infty + \varepsilon_1^B x_B + J_2^B x_B^2$$

$$\text{Excess } \Delta G_{\text{mixing}} = RT(x_A \ln(\gamma_A) + x_A \ln(\gamma_B))$$

$$\text{Excess } \Delta S_{\text{mixing}} = -R(x_A \ln(\gamma_A) + x_A \ln(\gamma_B))$$

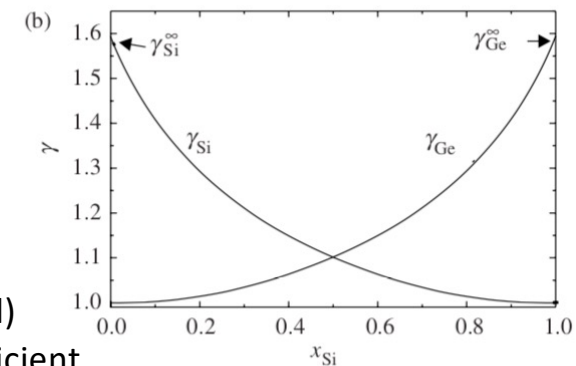

**This is similar to a virial expansion**

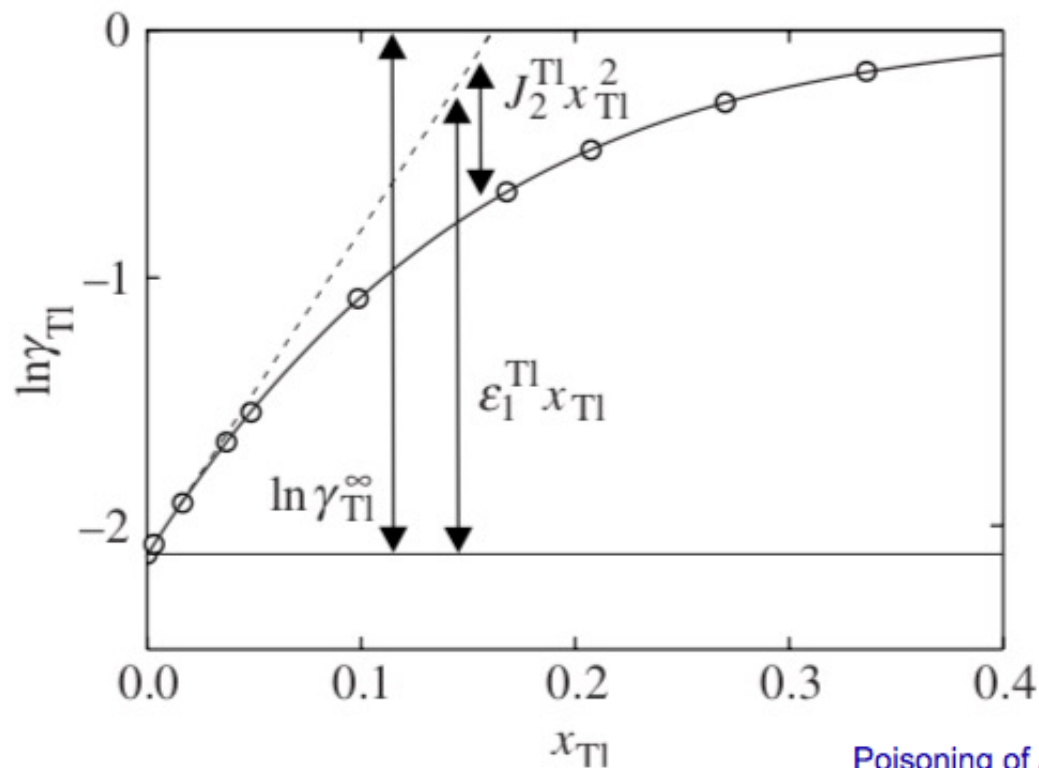

Thallium/Mercury

Lower freezing point  
of Mercury for  
thermometer and  
switches 8.5% -60°C  
versus -40°C

Also Rat poison

Poisoning of Alexander Litvinenko - Wikipedia

**Figure 3.9** An illustration of low-order terms in the Taylor series expansion of  $\ln \gamma_i$  for dilute solutions using  $\ln \gamma_{\text{Tl}}$  for the binary system Tl-Hg at 293 K as example. Here  $\ln \gamma_{\text{Tl}}^{\infty} = -2.069$ ,  $\epsilon_1^{\text{Tl}} = 10.683$  and  $J_2^{\text{Tl}} = -14.4$ . Data are taken from reference [8].

## Hildebrand Regular Solution Model

The change on mixing:

$$\Delta S = -nk_B (x_A \ln(x_A) + x_B \ln(x_B)) \text{ Ideal Solution}$$

Since  $(\ln x)$  is always negative or 0,  $\Delta S$  is always positive for ideal solutions

$$\Delta G = \Delta H - T \Delta S$$

Since  $(\ln x)$  is always negative or 0,  $\Delta G$  is positive or negative depending on  $\Delta H$  :: can **mix or demix**

Depending on the sign of  $\Delta H$

$\Delta V = (d\Delta G/dp)_T = 0$ , there is no loss or gain of volume compared to the summed volume

$$\Delta H = n \Omega x_A x_B$$


$\Omega$  is the interaction coefficient or regular solution constant

Molar Gibbs free energy of mixing

$$\Delta G_m = RT(x_A \ln(x_A) + x_B \ln(x_B)) + \Omega x_A x_B$$

$$\Omega = zN_A[u_{AB} - (u_{AA} + u_{BB})/2]$$

The equation is symmetric

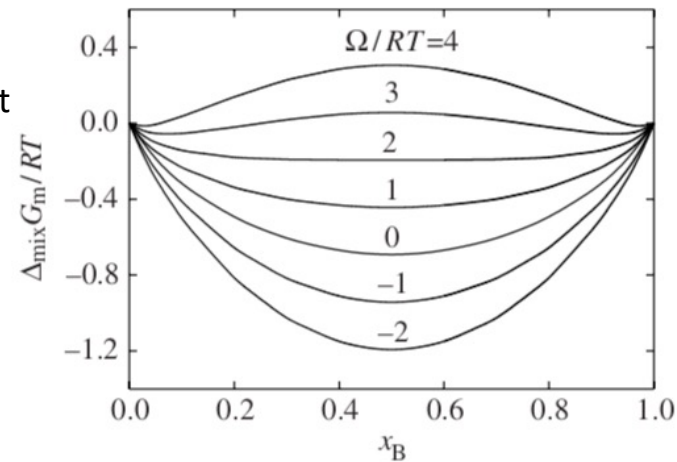

**Figure 3.10** The molar Gibbs energy of mixing of a regular solution A–B for different values of  $\Omega/RT$ .



### Hildebrand solubility parameter, $\delta$

$$\Delta H = n \Omega x_A x_B$$

$\Omega$  is the interaction coefficient or regular solution constant

Molar Gibbs free energy of mixing

$$G_m = RT(x_A \ln(x_A) + x_B \ln(x_B)) + \Omega x_A x_B$$

$$\Omega = zN_A[u_{AB} - (u_{AA} + u_{BB})/2]$$

$$\Delta H_m = \frac{\chi \varphi_A \varphi_B kT}{V_0}$$

Flory-Huggins chi parameter,  $\sim \Omega/kT$

$$\chi = \frac{V_0 V_M}{kT} (\delta_{T,A} - \delta_{T,B})^2 \quad \delta_T = \sqrt{\text{CED}} = \sqrt{\frac{E_{\text{coh}}}{V}}$$

Hansen solubility parameters

$$\chi = \frac{V_0 V_M}{kT} [(\delta_{D,A} - \delta_{D,B})^2 + (\delta_{P,A} - \delta_{P,B})^2 + (\delta_{H,A} - \delta_{H,B})^2] \quad \delta_D = \sqrt{\frac{E_{\text{coh,D}}}{V}}, \quad \delta_P = \sqrt{\frac{E_{\text{coh,P}}}{V}}, \quad \delta_H = \sqrt{\frac{E_{\text{coh,H}}}{V}}$$

## Hildebrand Solubility Parameter, $\delta$

Two materials with similar  $\delta$  are miscible

by Hildebrand and Hansen.<sup>15,16</sup> The Hildebrand solubility parameter ( $\delta_T$ ) is the square root of cohesive energy density (CED), and the CED is simply the cohesive energy ( $E_{coh}$ ) per unit of volume ( $V$ ):<sup>17</sup>

$$\delta_T = \sqrt{CED} = \sqrt{\frac{E_{coh}}{V}} \quad (1)$$

The intermolecular interactions are composed of dispersive ( $E_{coh,D}$ ), polar ( $E_{coh,P}$ ), and hydrogen bonding ( $E_{coh,H}$ ) interactions, so the Hansen solubility parameters ( $\delta_i$ ,  $i = D, P, H$ ) were proposed as follows:<sup>18</sup>

$$\delta_D = \sqrt{\frac{E_{coh,D}}{V}}, \quad \delta_P = \sqrt{\frac{E_{coh,P}}{V}}, \quad \delta_H = \sqrt{\frac{E_{coh,H}}{V}} \quad (2)$$

Then the relation between Hansen and Hildebrand solubility parameters as follows:

$$\delta_T^2 = \delta_D^2 + \delta_P^2 + \delta_H^2 \quad (3)$$

London dispersion forces (attractive)

Luo Y, Chen X, Wu S, Ca S Luo Z, Shi Y, *Molecular Dynamics Simulation Study on Two-Component Solubility Parameters of Carbon Nanotubes and Precisely Tailoring the Thermodynamic Compatibility between Carbon Nanotubes and Polymers*, *Langmuir* **36** 9291-9305 (2020).

$$\Delta G_m = \Delta H_m - T\Delta S_m$$

$$\Delta H_m = \frac{\chi \varphi_A \varphi_B kT}{V_0} \quad \text{Flory-Huggins Equation}$$

$\chi \sim 1/T$

$$\Delta H_m = \varphi_A \varphi_B (\delta_{T,A} - \delta_{T,B})^2 V_M$$

Hildebrand and Scratchard

$$\chi = \frac{V_0 V_M}{kT} (\delta_{T,A} - \delta_{T,B})^2$$

$$\chi = \frac{V_0 V_M}{kT} [(\delta_{D,A} - \delta_{D,B})^2 + (\delta_{P,A} - \delta_{P,B})^2 + (\delta_{H,A} - \delta_{H,B})^2]$$

## Asymmetric equations for asymmetric phase diagram

Sub-regular solution model

$$\Delta_{\text{mix}}^{\text{exc}} G_{\text{m}} = x_{\text{A}} x_{\text{B}} (A_{21} x_{\text{A}} + A_{12} x_{\text{B}})$$


$$\ln \gamma_1 = x_2^2 [A_{12} + 2(A_{21} - A_{12})x_1] ; \text{ similarly } \ln \gamma_2 = x_1^2 [A_{21} + 2(A_{12} - A_{21})x_2]$$

$$A_{12} = \left(2 - \frac{1}{x_2}\right) \frac{\ln \gamma_1}{x_2} + \frac{2 \ln \gamma_2}{x_1} \quad A_{21} = \left(2 - \frac{1}{x_1}\right) \frac{\ln \gamma_2}{x_1} + \frac{2 \ln \gamma_1}{x_2}$$

$$\Delta_{\text{mix}}^{\text{exc}} G_{\text{m}} = \sum_{i=1}^m \sum_{j=1}^n x_{\text{A}}^i x_{\text{B}}^j A_{ij}$$

Redlich-Kister Expression

$$\Delta_{\text{mix}}^{\text{exc}} G_{\text{m}} = x_{\text{A}} x_{\text{B}} [\Omega + A_1(x_{\text{A}} - x_{\text{B}}) + A_2(x_{\text{A}} - x_{\text{B}})^2 + A_3(x_{\text{A}} - x_{\text{B}})^3 + \dots]$$

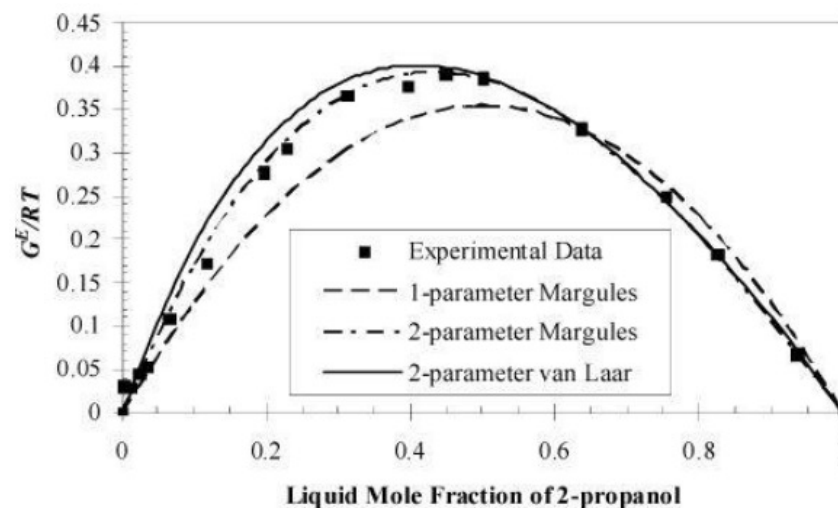

**Figure 11.3. Illustration of calculation of  $G^E$  from experiment and fitting of Margules models to a single point as discussed in [Examples 11.1](#) and [11.5](#), for 2-propanol + water, with the experimental data points from [Fig. 10.8](#) on page [395](#). Data are tabulated in [Example 11.8](#). The van Laar model fit to a single point is explained in [Section 12.2](#).**

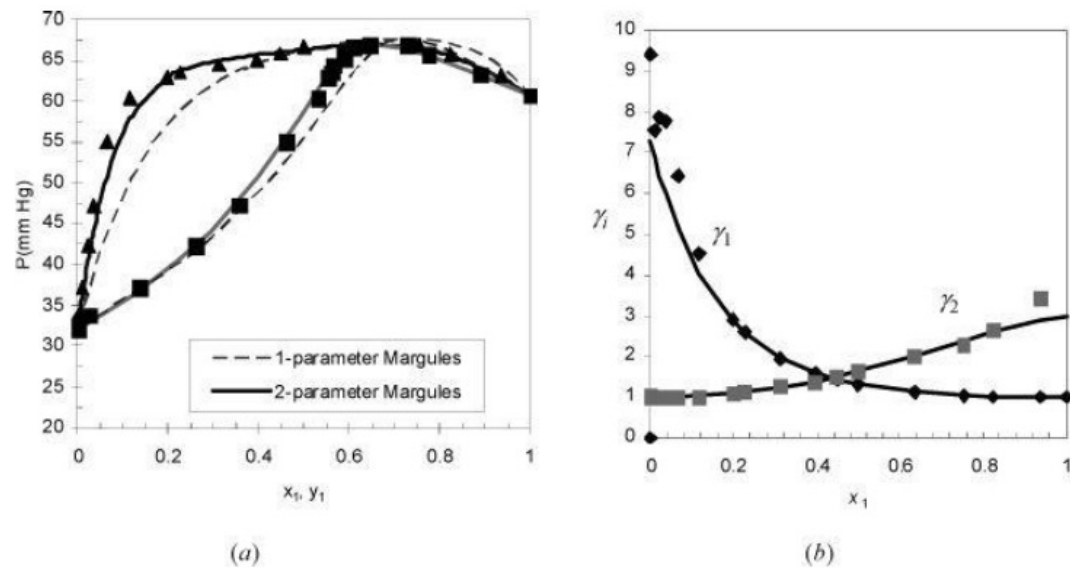


Figure 11.5. (a) One-parameter and two-parameter Margules equation fitted to a single measurement in [Examples 11.2](#) and [11.5](#) compared with the experimental data points from [Fig. 10.8](#) on page 395. Data are tabulated in [Example 11.8](#). (b) Activity coefficients predicted from the parameters fitted in [Example 11.5](#) compared with points calculated from the data.

**Non-ideal entropy of mixing**  
**Quasi-regular solution model**

$$\Delta_{\text{mix}}^{\text{exc}} G_{\text{m}} = x_{\text{A}} x_{\text{B}} \Omega \left( 1 - \frac{T}{\tau} \right)$$

$$\Delta_{\text{mix}}^{\text{exc}} S_{\text{m}} = - \frac{\partial(\Delta_{\text{mix}}^{\text{exc}} G_{\text{m}})}{\partial T} = x_{\text{A}} x_{\text{B}} \left( \frac{\Omega}{\tau} \right)$$

**This is a non-combinatorial entropy**

This would occur if there were ordering on mixing, say when you add oil to water. The enthalpy of mixing favors mixing!!! Water organizes at the surface of oil to a great extent; this reduces entropy and makes oil and water demix. Water actually “likes” oil. This is called the “*hydrophobic effect*” and is an important concept for protein folding.


## Graphical Method to Estimate Chemical Potential

Does  $dG/dx_i = dG/dn_i = \mu_i$ ?

**No**

$$dG/dn_i = dG/dx_i \, dx_i/dn_i$$

$$dx_i/dn_i = d(n_i/(n_i+n_j))/dn_i = 1/(n_i+n_j) - n_i/(n_i+n_j)^2$$

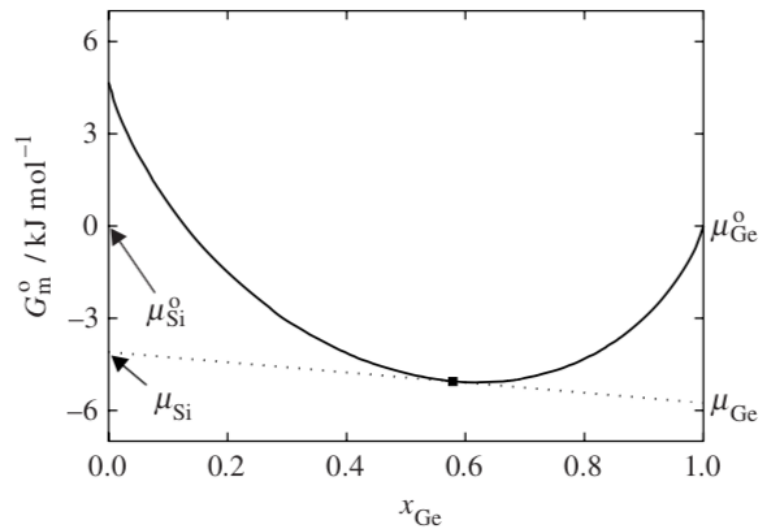

**Figure 3.12** The integral molar Gibbs energy of liquid Ge–Si at 1500 K with pure liquid Ge and solid Si as standard states. Data are taken from reference [4].

## Solving the Regular Solution Model

We know that the excess Gibbs free energy for mixing is given by:

$$G^E/RT = x_A \ln \gamma_A + x_B \ln \gamma_B \quad \text{Generic expression using activity coefficient}$$

And we have defined for the regular solution model that

$$G^E/RT = \Omega x_A x_B \quad \text{Hildebrand Regular Solution expression}$$

If we propose the answer  $RT \ln \gamma_A = \Omega x_B^2$

We find by substitution generic expression that it equals the regular solution expression since  $x_B + x_A = 1$   
(Solving this directly **see next slide.**)

$$\frac{\Delta_{\text{mix}}^{\text{exc}} \bar{G}_A}{RT} = \ln \gamma_A = \frac{\Omega}{RT} x_B^2$$


$$\frac{\Delta_{\text{mix}}^{\text{exc}} \bar{G}_B}{RT} = \ln \gamma_B = \frac{\Omega}{RT} x_A^2$$



$$G^E = RT \sum_i x_i \ln(\gamma_i)$$

## Activity Coefficients as Derivatives

$$\left( \frac{\partial G^E}{\partial n_i} \right)_{T, P, n_{j \neq i}} = \bar{G}_i^E = \mu_i^E = RT \ln \gamma_i$$

11.28  Activity coefficients are related to the partial molar excess Gibbs energy.

$$\frac{G^E}{RT} = A_{12} x_1 x_2 \qquad \frac{G^E}{RT} = n(A_{12} x_1 x_2) = (A_{12} n_2) \left( \frac{n_1}{n} \right) \qquad 11.29$$

$$\frac{1}{RT} \left( \frac{\partial G^E}{\partial n_1} \right)_{T, P, n_2} = \ln \gamma_1 = A n_2 \left[ \frac{1}{n} - \frac{n_1}{n^2} \right] = A \frac{n_2}{n} \left[ 1 - \frac{n_1}{n} \right] = A x_2 (1 - x_1) \qquad 11.30$$

$$\ln \gamma_1 = A x_2^2 \text{ ; similarly } \ln \gamma_2 = A x_1^2 \qquad 11.31$$

## Use of the Gibbs-Duhem Equation to determine the activity of a component

$$n_A d\mu_A + n_B d\mu_B = 0 \quad \text{Constant } p, T$$

$$x_A d \ln a_A + x_B d \ln a_B = 0$$


$$x_A d \ln x_A + x_A d \ln \gamma_A + x_B d \ln x_B + x_B d \ln \gamma_B = 0$$

$$x_A d \ln x_A + x_B d \ln x_B = x_A \frac{dx_A}{x_A} + x_B \frac{dx_B}{x_B} = dx_A + dx_B = 0$$

$$x_A d \ln \gamma_A + x_B d \ln \gamma_B = 0 \quad \text{Restatement of Gibbs-Duhem for Solutions}$$

If you know  $\gamma_A$  you can obtain  $\gamma_B$  by integration

$$\ln \gamma_B - \ln \gamma_B(x_B = 1) = - \int_{x_B=1}^{x_B} \frac{x_A}{x_B} d \ln \gamma_A$$

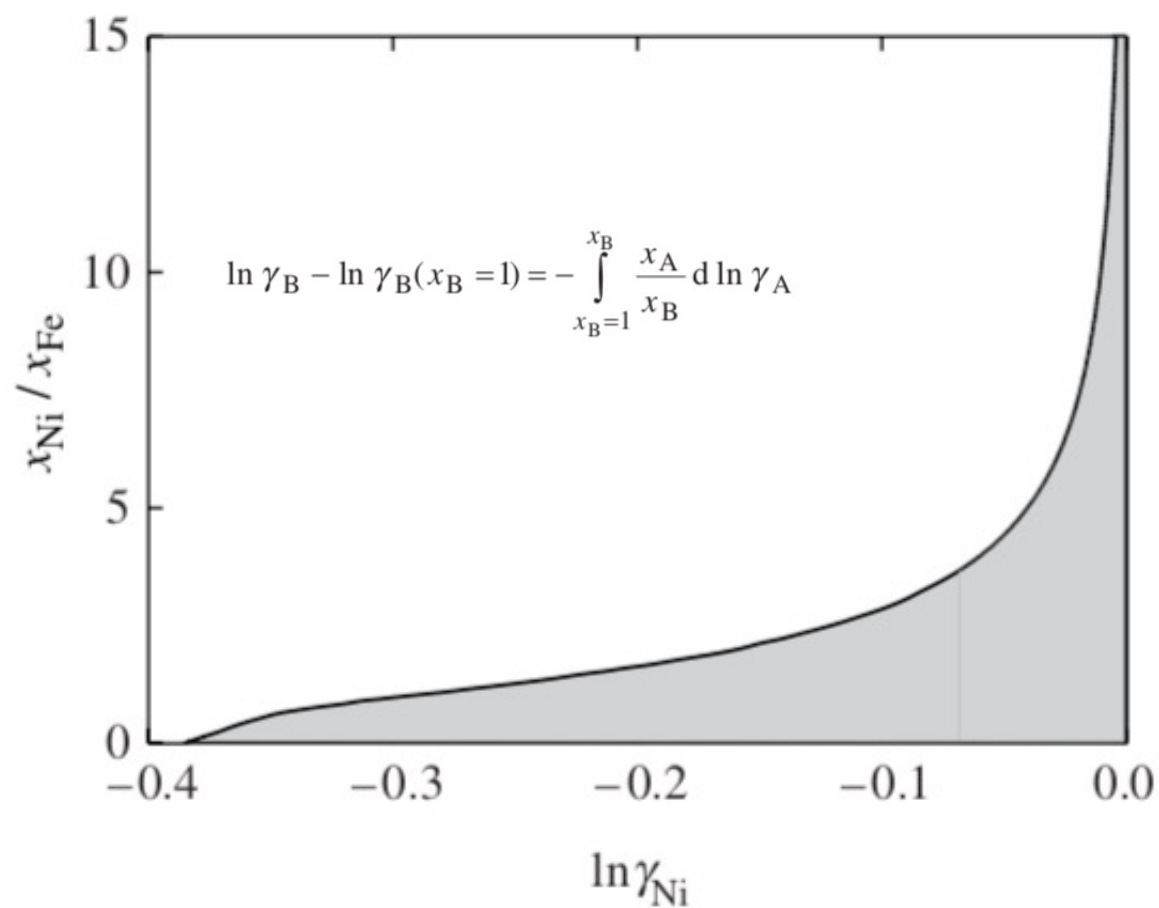

**Figure 3.13**  $x_{\text{Ni}}/x_{\text{Fe}}$  versus  $\ln \gamma_{\text{Ni}}$  of molten Fe–Ni at 1850 K. Data are taken from reference [3].

